

The Synthesis of Ternary Acetylides with Tellurium: Li_2TeC_2 and Na_2TeC_2

Károly Németh,^{*,†} Aditya K. Unni,^{*,‡} Christopher Kalnmals,[‡] Carlo U. Segre,[¶] and
James Kaduk[‡]

*Physics Department, Illinois Institute of Technology, Chicago, Illinois 60616, USA, Department
of Chemistry, Illinois Institute of Technology, Chicago, Illinois 60616, USA, and Physics
Department and CSRRI, Illinois Institute of Technology, Chicago, Illinois 60616, USA*

E-mail: nemeth@phys.iit.edu; aunni@iit.edu

Abstract

The synthesis of ternary acetylides Li_2TeC_2 and Na_2TeC_2 is presented as the first example of ternary acetylides with metalloid elements instead of transition metals. The synthesis was carried out by the direct reaction of the corresponding alkali acetylides with tellurium powder in liquid ammonia. Alternatively, the synthesis of Na_2TeC_2 was also carried out by the direct reaction of tellurium powder and two equivalents of NaC_2H in liquid ammonia leading to Na_2TeC_2 and acetylene gas through an equilibrium containing the assumed NaTeC_2H molecules besides the reactants and the products. The resulting crystalline materials were characterized by x-ray diffraction. Implications of these new syntheses on the synthesis of other ternary acetylides with metalloid elements and transition metals are also discussed.

^{*}To whom correspondence should be addressed

[†]Illinois Institute of Technology

[‡]Illinois Institute of Technology

[¶]Illinois Institute of Technology

Introduction

Ternary alkali metal (A) transition metal (M) acetylides with a general formula A_2MC_2 or AMC_2 have been the subject of research in inorganic and coordination chemistry for a few decades.¹⁻⁶ Ternary acetylides synthesized so far involve AMC_2 compounds with $A \in \{\text{Li, Na, K, Rb, Cs}\}$ and $M \in \{\text{Cu, Ag, Au}\}$ and A_2MC_2 compounds with $A \in \{\text{Na, K, Rb, Cs}\}$ and $M \in \{\text{Pt, Pd}\}$. A major source of synthesis methods and characterization results on ternary acetylides is from the Ruschewitz group.^{1,3,7-12} It was theoretically predicted in a recent publication by Terdik, Németh, Harkay *et al*¹³ that the photoemissive properties of Cs_2Te , an old photoemissive material with very high quantum efficiency, could be improved by acetylation leading to a predicted Cs_2TeC_2 material. Related compounds, such as Na_2TeC_2 , might have similarly advantageous photoemissive properties, such as high quantum-efficiency and reduced workfunction as calculated for the parent alkali tellurides. Existing A_2MC_2 ternary acetylides are built of linear polymeric chains with $-M-C\equiv C-$ repeating units embedded in a matrix of alkali cations. The existence of such chains with $-Te-C\equiv C-$ repeating units was proposed by the above-mentioned theoretical study, motivated by knowledge of A_2MC_2 compounds. Analogous monomeric acetylenic tellurides/selenides/sulfides with the $R-C\equiv C-(Te/Se/S)-C\equiv C-R'$ structure have been known for decades.^{4,14,15} Note, however, that in A_2MC_2 crystals the M atoms are formally neutral, and the $-M-C\equiv C-$ repeating units carry a charge of negative two that is charge-balanced by two adjacent alkali cations, as compared to the charge neutral $R-C\equiv C-(Te/Se/S)-C\equiv C-R'$ species where the formal oxidation state of the chalcogen is +2. Alternatively, in the A_2TeC_2 systems developed in this study, the $-Te-C\equiv C-$ repeating unit must carry a -2 charge. While binary transition metal acetylides with the formula MC_2 are well known explosives, their alkalinated versions AMC_2 and A_2MC_2 are not explosive, however, they are very air and moisture sensitive as they are strong reducing agents.¹ In fact, it is because of their strong reducing nature that $LiAuC_2$ and $LiAgC_2$, the only known Li-containing ternary acetylides^{7,8} have even been proposed as anode materials for Li-ion batteries.¹⁶ Developing new syntheses of ternary acetylides with lighter and abundant transition metals or metalloids would allow for their practical consideration as anode materials in Li/Na-ion batteries. The goal of the

present work was to develop an alternative synthesis to these intriguing materials, and determine the structure of a new class of tellurium containing ternary acetylides.

Experimental Section

Synthesis of Li_2TeC_2 from Li_2C_2 and Te

Li_2C_2 was synthesized by the reaction of Li metal and acetylene gas in liquid ammonia (lq-NH_3), followed by spontaneous disproportionation of LiC_2H to Li_2C_2 and acetylene gas upon evaporation of the ammonia, and warming to ambient temperature, as described e.g. in Ref. 3. In a N_2 glovebox, tellurium powder (384 mg, 3 mmol) as obtained from Sigma-Aldrich (99.8 %) was mixed with Li_2C_2 powder (120 mg, 3.17 mmol, 5.5 % excess) in a flame-dried 100 ml Schlenk flask with a Teflon plug valve, then sealed and brought into a fume hood. NH_3 gas from a tank was condensed at $\approx -60^\circ\text{C}$ until it fully covered the solid reactants. The chilling of the flask was carried out in an acetone bath placed in a sonicator bay (Branson Model 3510 Ultrasonic Cleaner) through a coil attached to an electric laboratory chiller. Sonication of the reactants was started when they were completely covered by lq-NH_3 (5-10 mL). The sonication and condensation of NH_3 (at a slightly higher than atmospheric pressure) continued until all the Te powder was consumed by the reaction. The flask was occasionally swirled by hand and lifted out of the bath to confirm the disappearance of the Te powder at the bottom of the flask. Depending on the concentration of the reactants in the lq-NH_3 , complete consumption of the Te typically took 10-30 minutes. The color of the reaction mixture gradually changed from purple to violet and finally to yellow. When the Te was fully consumed, the flask was gradually warmed to room temperature and the NH_3 carefully evaporated. The flask was then sealed under a NH_3 atmosphere and brought into the glove box for handling and storage.

Synthesis of Na₂TeC₂ from Na₂C₂ and Te


Na₂C₂ was synthesized by the reaction of elemental sodium and acetylene gas in lq-NH₃ followed by heating the resulting NaC₂H at 155 °C under vacuum as described in Ref. 17. The reaction of Te powder (384 mg, 3 mmol) with Na₂C₂ powder (220 mg, 3.14 mmol, 5 % excess) in lq-NH₃ was carried out analogously to that of the above described synthesis of Li₂TeC₂. The resulting product is a yellow powder that also has to be handled in an inert atmosphere.

Synthesis of Na₂TeC₂ from NaC₂H and Te

NaC₂H was synthesized by the direct reaction of Na (200 mg, 8.70 mmol) with acetylene gas in lq-NH₃ using a 100 ml Schlenk flask as above. Tellurium powder (520 mg, 4.06 mmol) was added to the dry NaC₂H under protective flow of NH₃ gas and lq-NH₃ was condensed again on the reactants. The flask was occasionally manually swirled to allow for better mixing of the reactants. The Te powder was consumed in about 10 minutes without sonication producing a yellowish solution with some yellowish precipitates. The NH₃ solvent was carefully evaporated and a pale yellow powder obtained. The sealed Schlenk flask was brought in the glove box and its contents were scraped into a mortar and ground whereby they became a yellow powder. Powder x-ray diffraction confirms that the materials obtained by the two different syntheses of Na₂TeC₂ are identical.

Synthesis of Tellurium Acetylide, TeC₂

We have also attempted to synthesize the binary acetylide TeC₂ polymer by the polycondensation reaction of diiodoacetylene¹⁸ and lithium telluride¹⁹ in dry tetrahydrofuran, according to



The reaction product was a metallic gray powder that was extremely sensitive to mechanical agitation after being washed with water and diethyl ether on filter paper. When dry, this material violently decomposed upon contact with a spatula. Because of its explosivity that is similar to

that observed in transition metal acetylides, this product could not be characterized.

Synthesis of Ph-C $\equiv$ C-Te-C $\equiv$ C-Ph and its double lithiated form

Bis(phenylethynyl)telluride, Ph-C $\equiv$ C-Te-C $\equiv$ C-Ph, was synthesized following the procedure of Ref. 20, starting from phenylacetylene (Sigma Aldrich). We have also attempted to synthesize its double lithiated form, in analogy to the A₂TeC₂ ternary acetylides, reacting Li-Ph-acetylide (Ph-C $\equiv$ C⁻Li⁺) with Te powder in a 2:1 molar ratio in a sonicated dry THF solution. After about 24 hours of sonication all the Te powder was consumed. Evaporation of THF resulted in a yellow powder which turned out to be a 1:1 molar mixture of Ph-C $\equiv$ C-Te⁻Li⁺ and unreacted Ph-C $\equiv$ C⁻Li⁺, as characterized by Extended X-ray Absorption Fine Structure (EXAFS) spectroscopy. This indicates that the hypothesized salt Li₂[Ph-C $\equiv$ C-Te-C $\equiv$ C-Ph] does not form, and the negatively charged -C $\equiv$ C-Te-C $\equiv$ C- structural units are stable only in the A₂TeC₂ ternary acetylides.

X-ray diffraction based characterization

Powder x-ray diffraction (XRD) spectra of the materials produced were obtained on a Bruker D2 Phaser benchtop XRD system using Cu-K α ₁ radiation at 1.5406 Å wavelength, at room temperature. An air-tight PMMA specimen holder with a dome (Bruker A100B33) was used to hold the air-sensitive materials during the measurements. This sample holder adds a large background to the measured spectra between 15 and 25 (°) 2 Θ values. Note that XRD data for 2 Θ values smaller than those shown in Figs. 1 and 2 are all due to the sample holder, including a sharper peak at about 13 and a broader one at about 10 (°) 2 Θ . Crystal structures were refined using the GSAS software package.²¹

EXAFS based characterization

Extended X-ray Absorption Fine Structure (EXAFS) spectroscopy measurements were carried out on Ph-C $\equiv$ C-Te-C $\equiv$ C-Ph and its double lithiated form at the Te K α edge using synchrotron radia-

tion at the MRCAT (Sector 10) beamline of the APS facility at Argonne National Laboratory. Data was processed using the IFEFFIT-based programs Athena and Artemis.^{22,23}

Results and Discussion

All previously known ternary acetylides of the A_2MC_2 type were synthesized by the solid state reaction of the corresponding bialkali acetylides and Pt or Pd sponges:^{9–11}



As our initial attempts to follow the solid state reaction method failed for the direct reaction of tellurium powder with Li_2C_2 , we had been looking for a suitable solvent to carry out the same reaction.

A recent article by the Ruschewitz group pointed out that (bi)alkali acetylides actually dissolve to some extent in liquid ammonia ($lq-NH_3$).¹² The same study also suggested that $lq-NH_3$ might be a suitable reaction medium for the synthesis of ternary acetylides. Motivated by this publication, we attempted the direct reaction of Te powder with slight molar excess of Li_2C_2 or Na_2C_2 in $lq-NH_3$. The rather quick dissolution of the Te powder during the reaction indicated the reaction of the dialkali acetylides with the Te metal, as no dissolution occurs in the absence of the acetylides. When run in an ultrasonicator, the Te was completely consumed in 10–30 minutes, depending on the concentration of the reactants. Ultrasonication significantly shortens the time needed for completing the consumption of Te powder by the bialkali acetylide, as compared to simple stirring (2–3 hours). We have used various temperatures from -80 to -35 °C and the reaction always completed very quickly when sonication was used. We have also tried using dry tetrahydrofuran and diethyl ether as a reaction solvent but these proved far inferior to $lq-NH_3$ and resulted only in some discoloration of the reactants even after hours of sonication.

The synthesis starts with the condensation of ammonia onto a mix of the Te and bialkali acetylide powder in a suitable, dry reaction vessel, such as a Schlenk flask. In the initial phase

of the condensation, when there is only a small amount of lq-NH_3 present, purple/violet/red colors can be observed in the reaction mixture. These colors are typical indicators of polytelluride cluster anions that dissolve well in lq-NH_3 , as known for a century.¹⁹ Such polytelluride anions may consist of tens of Te atoms in a single cluster carrying typically only a negative charge or two.¹⁹ In the case of our reactions, the charge of these Te clusters may only come from acetylide ions that attack the Te powder from the solution and split it up into cluster anions with attached acetylide units that dissolve in lq-NH_3 . As the dissolution of binary acetylides in lq-NH_3 is very limited,¹² one might expect a slow reaction. However, the small amount of dissolved acetylides is sufficient to solubilize all the tellurium powder and then it will be the dissolved polytelluride anions that attack the solid crystallites of bialkali acetylides to further split the polytelluride anions until all acetylide ions are attached to Te atoms or clusters. Thus, the solubility of polytelluride ions allows for an autocatalytic process and the reaction goes quickly even at low temperature, especially when sonication assists the mixing of the reactants and their attacks on each other.


The final product is a colloid of yellow Li_2TeC_2 or Na_2TeC_2 crystallites in lq-NH_3 , which must be stored air-free after the evaporation of NH_3 and handled in a glove-box, as the products are very air and moisture sensitive, similar to their transition metal analogues.

The application of large (around 50 %) molar excess Te instead of excess acetylide results in a cherry red solution of dissolved species. In this case the complete dissolution of the Te powder may take a longer period of sonication and is believed to produce polytelluride ions with attached acetylide units.

While Li_2C_2 is easy to produce due to the spontaneous disproportionation of LiC_2H at room temperature, the production of heavier bialkali acetylides is increasingly cumbersome, especially for $A \in \{\text{K}, \text{Rb}, \text{Cs}\}$ as it involves high temperature heating of monoalkali acetylides mixed with alkali metals in high vacuum.^{3,12} To avoid the direct use of bialkali acetylides we have developed an alternative synthesis based on monoalkali acetylides only. It consists of first reacting the Te powder with two molar equivalent of monoalkali acetylides according to



that is followed by the disproportionation of the resulting mixture:



The first step of this reaction is familiar from analogous acetylenic organo-telluride reactions when the H of $ATeC_2H$ is replaced by an organic functional group, typically an arene.^{14,15,20} The second step may largely complete when the solvent NH_3 is evaporated along with the acetylene gas, with the possibility that the rest of the acetylene gas is removed when the product is ground in a mortar. A repeated condensation of NH_3 and sonication of the mixture, followed by repeated evaporation of NH_3 helps to better mix the reaction components and remove as much residual acetylene gas as possible, before grinding the product in a mortar. We have not characterized $ATeC_2H$, as the above two reactions are part of an equilibrium and the isolation of $ATeC_2H$ appeared difficult, if at all possible. The identity of the products for both Na_2TeC_2 syntheses are indicated by overlapping powder x-ray diffraction (XRD) spectra. The monoalkali acetylide based synthesis of ternary acetylides may be applicable to the synthesis of a wide variety of ternary acetylides avoiding the cumbersome production of heavier bialkali acetylides and the use of high-temperature solid state reactions.

Powder XRD spectra of Li_2TeC_2 and Na_2TeC_2 as well as the comparison of XRD patterns of Na_2TeC_2 made by the two different synthesis routes described above are shown in Figures 1, 2 and 3, respectively. The main geometric parameters of Li_2TeC_2 and Na_2TeC_2 , as obtained from Rietveld fitting of XRD data, are listed in Table 1. Full details of the fitting are available as supplementary material.²⁴ Note that XRD data for 2Θ values smaller than those shown in Figs. 1 and 2 are all due to the sample holder, including a sharper peak at about 13 and a broader one at about 10 ($^\circ$) 2Θ . Figures 4 and 5 display the fitted structures of Li_2TeC_2 and Na_2TeC_2 , respectively. The space group of Li_2TeC_2 is $P\bar{3}m1$, identical with the space group of all known A_2MC_2 ($M=Pt, Pd$;

A=Na,K,Rb,Cs) compounds. The space group of Na_2TeC_2 , however, is $I4/mmm$, representing a new structure in ternary acetylides. Also note that the fitting of Na_2TeC_2 data identified two phases, a major one of the actual Na_2TeC_2 material with $I4/mmm$ space group and a minor one of the unreacted excess Na_2C_2 used in the synthesis.

The $\text{C}\equiv\text{C}$ distance in Li_2TeC_2 is 1.044 Å, interpreted as a projection of a wobbling $\text{C}\equiv\text{C}$ dumbbell onto the c axis, therefore it is shorter than an acetylenic bond ($\text{C}\equiv\text{C}$ distance is 1.203 Å in acetylene gas). The $\text{C}\equiv\text{C}$ distance in Na_2TeC_2 , as projected on the a and b axes, is 1.208 Å very close to that in acetylene. The wobbling motion of the $\text{C}\equiv\text{C}$ dumbbell and its effect on the projected $\text{C}\equiv\text{C}$ distance has also been observed in other ternary acetylides, such as K_2PdC_2 .¹⁰ The short, 1.727 Å, Te-C distance in Li_2TeC_2 should also be interpreted as a projected distance, while the long, 2.333 Å, Te-C distance in Na_2TeC_2 is closer to expectations based on DFT predictions.¹³ The Te-C distance in bis[(4-methylphenyl) ethynyl] telluride is 2.045 Å,²⁰ while it is expected to be about 2.4 Å in ternary acetylides with Te on the basis of DFT calculations, assuming the $P\bar{3}m1$ space group.¹³ The surprisingly large a/c ratio in Li_2TeC_2 and the large Li-Te and Li-C distances appear to correlate with the above mentioned wobbling motion of the $\text{C}\equiv\text{C}$ unit around the c -axis and may explain also the broad peaks in the XRD spectra. The broadness of the observed XRD spectral lines may partially also be attributed to crystal defects that may occur due to the low temperature of the synthesis where the crystal structure can not anneal well.

In the present phase of our research on ternary acetylides with tellurium, our only method of characterization was x-ray diffraction of the freshly made samples shortly after the synthesis, using an air-tight PMMA sample holder. We have also attempted to obtain synchrotron XRD data of the same samples: unfortunately, the samples partially decomposed during the storing and handling, this was indicated by significant additional peaks in the synchrotron XRD spectra, as compared to the locally measured ones. Neutron diffraction would also be very useful, especially for Li_2TeC_2 , for a more precise determination of the Li and C positions, as Te has a much greater x-ray scattering factor. The measurement of Raman spectra would be helpful in the characterization of the $\text{C}\equiv\text{C}$ bond and C^{13} NMR to the types of carbon atoms present.

The above types of additional characterizations could not be carried out in the present work primarily for reasons of great air-sensitivity of the product materials. They will be subject of forthcoming investigations. However, we are still confident that we have identified the title new compounds solely on the basis of the presented XRD data and through the control of the stoichiometries of the reactants. The XRD spectra of related compounds, such as A_2O , AOH , A_2Te , A_2Te_2 , Te , A_2C_2 and AC_2H ($A = Li, Na$, with the exception of Li_2Te_2 that is not known¹⁹⁾) are so clearly distinct from the observed XRD spectra, that none of them was found to be present in the syntheses products, except a small amount of the alkali acetylides used in excess as reactants.

We have not taken elemental analysis of the products either, as the purity of the reagents was confirmed by XRD analysis and the solvent $lq-NH_3$ is not expected to react with them at the low temperatures applied and is unlikely to form stable complexes with Li^+ or Na^+ at room temperature as ammonia complexes of alkali acetylides are known to exist only at the low temperatures of $lq-NH_3$ ¹² and would decompose when warmed up to room temperature. Therefore the total stoichiometry of the products should be the same as that of the reactants with the exception of the reaction using NaC_2H as reactant. In this latter case, however, the identity of the diffraction patterns shown in Fig. 3 indicates identical composition of the products of the two different syntheses referenced in the same Figure, which makes the disproportionation of NaC_2H to Na_2C_2 and H_2C_2 as described in Eqs. ?? and ?? the only possible explanation of this reaction even without the explicit detection of H_2C_2 in the gases when the $lq-NH_3$ solvent is evaporated.

It is well known that Zintl anions (polyanions) of heavier p-field elements, such as Te, Se, As, Sb, Bi, Pb , etc, are highly soluble in $lq-NH_3$ (for reviews see e.g. Refs. 25,26). Such polyanions have also been observed with some transition metal elements, such as Hg .²⁵ This solubility of the Zintl anions in $lq-NH_3$ suggests that more ternary acetylides with metalloid and transition metal elements may be synthesized in $lq-NH_3$ following analogous procedures to the ones described herein for Te -containing ternary acetylides. In principle, these procedures may work also for transition metals if the transition metal starting material is provided in the form of sufficiently small polyatomic clusters, for example in the form of pyrophoric iron, nickel, manganese, etc. This may

provide a practical route for the production and use of ternary acetylides, for example as anode materials in Li-ion batteries.

In order to test whether the charged bis(ethynyl) tellurides exist in a molecular form as well, we have synthesized $\text{Ph-C}\equiv\text{C-Te-C}\equiv\text{C-Ph}$ following Ref. 20 and its hypothetical double lithiated form, $\text{Li}_2[\text{Ph-C}\equiv\text{C-Te-C}\equiv\text{C-Ph}]$, by the direct reaction of $\text{Ph-C}\equiv\text{C}^-\text{Li}^+$ with Te powder in a 2:1 molar ratio in sonicated dry THF solution. Figure 6 shows a comparison of the Te K-edge EXAFS spectra of the two materials. The spectrum of $\text{Ph-C}\equiv\text{C-Te-C}\equiv\text{C-Ph}$ can be modeled up to $R = 3 \text{ \AA}$ by nominal structure which has two $\text{C}\equiv\text{C}$ groups surrounding the Te absorber (see supplementary material for details, Ref. 24). However the spectrum of $\text{Li}_2[\text{Ph-C}\equiv\text{C-Te-C}\equiv\text{C-Ph}]$ shows ca. 0.8 $\text{C}\equiv\text{C}$ groups surrounding each Te atom on average. This indicates that the product of the latter reaction is a less than 1:1 molar mixture of $\text{Ph-C}\equiv\text{C-Te}^-\text{Li}^+$ and unreacted $\text{Ph-C}\equiv\text{C}^-\text{Li}^+$, see Figure 6. This suggests that the negatively charged $-\text{C}\equiv\text{C-Te-C}\equiv\text{C}-$ bonding system exists only in the crystals of A_2TeC_2 ternary acetylides and not in molecular forms.

While the ternary acetylides synthesized in the present work may display many interesting physical properties, such as those predicted in Ref. 13 by Terdik, Németh, Harkay, et al., the present work was intended to discuss solely the synthesis of these new materials. The examination of their electronic properties, such as charge distribution, workfunction, photoemissive quantum yield and battery electrode applications should be the subject of separate investigations. We believe that the synthesis methods described here are significantly new as they allow for a quick solvent-based synthesis of A_2MC_2 type ternary acetylides instead of the traditional high temperature solid state synthesis. The key enabler of the new synthesis methods is the solubility of acetylated polyanionic clusters of tellurium atoms (or potentially that of other metalloid or metal elements) in lq-NH_3 , described in the present work for the first time in the literature. This development was also motivated by the recent observation of limited solubility of acetylide ions in lq-NH_3 by the Ruschewitz-group.¹²

Summary and Conclusions

We have described two efficient new synthesis methods for the production of ternary alkali metal tellurium acetylides, Li_2TeC_2 and Na_2TeC_2 . The new syntheses methods are based on the reaction of binary alkali acetylides with tellurium in lq-NH_3 , or on the reaction of tellurium powder with two equivalent of monoalkali acetylides in lq-NH_3 and letting the system disproportionate to the corresponding bialkali ternary acetylide and acetylene gas. This latter method avoids the cumbersome synthesis of heavier binary acetylides. The syntheses are significantly accelerated by ultrasonication. The colors of the reaction mixture point toward the existence of polyatomic tellurium anions with attached acetylene units dissolved in lq-NH_3 in earlier phases of the reactions. The good solubility of these polyanions in lq-NH_3 and the modest solubility of binary acetylides allow for fast reactions even at the low temperatures of the lq-NH_3 medium, especially when sonication is used, too. The ternary acetylides produced are the first examples of ternary acetylides with metalloid elements, as opposed to the numerous examples of previously synthesized ternary acetylides with Au, Ag, Cu, Pd and Pt. Furthermore, it is expected that these new syntheses may be used analogously to produce ternary acetylides with other metalloid and transition metal elements as well, provided that soluble polyatomic anions can be produced in early phases of the reactions.

Acknowledgements

The authors gratefully acknowledge technical help and discussions with Prof. A. Hock, Mr. M. Weimer, Mr. M. Foody and other members of the Hock group at IIT, as well as LiLi Kang and Songyang Han and other members of the Unni group and technical help from Dr. B. Shyam (SLAC/Stanford) and Prof. J. Terry (IIT). MRCAT operations are supported by the Department of Energy and the MRCAT member institutions. This research used resources of the Advanced Photon Source, a U.S. Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under Contract No. DE-AC02-06CH11357.

References

- (1) Ruschewitz, U. *Zeitschrift für anorganische und allgemeine Chemie* **2006**, 632, 705–719.
- (2) Buschbeck, R.; Low, P. J.; Lang, H. *Coordination Chemistry Reviews* **2011**, 255, 241–272.
- (3) Ruschewitz, U. *Coordination chemistry reviews* **2003**, 244, 115–136.
- (4) Brandsma, L.; Heus-Kloos, Y.; van der Heiden, R.; Verkruijsse, H. *Preparative acetylenic chemistry*; Elsevier, 1988.
- (5) Brandsma, L. *Best Synthetic Methods: Acetylenes, Allenes and Cumulenes: Acetylenes, Allenes and Cumulenes*; Best Synthetic Methods; Elsevier Science, 2003.
- (6) Stang, P.; Diederich, F. *Modern Acetylene Chemistry*; Wiley, 2008.
- (7) Kockelmann, W.; Ruschewitz, U. *Angewandte Chemie International Edition* **1999**, 38, 3492–3495.
- (8) Offermanns, J.; Ruschewitz, U.; Kneip, C. *Zeitschrift für anorganische und allgemeine Chemie* **2000**, 626, 649–654.
- (9) Ruschewitz, U. *Zeitschrift für anorganische und allgemeine Chemie* **2001**, 627, 1231–1235.
- (10) Billetter, H.; Wallraff, T.; Schwarz, U.; Smith, R. I.; Ruschewitz, U. *Zeitschrift für anorganische und allgemeine Chemie* **2010**, 636, 1834–1838.
- (11) Hemmersbach, S.; Zibrowius, B.; Kockelmann, W.; Ruschewitz, U. *Chemistry-A European Journal* **2001**, 7, 1952–1958.
- (12) Hamberger, M.; Liebig, S.; Friedrich, U.; Korber, N.; Ruschewitz, U. *Angewandte Chemie International Edition* **2012**, 51, 13006–13010.
- (13) Terdik, J. Z.; Németh, K.; Harkay, K. C.; Terry Jr, J. H.; Spentzouris, L.; Velázquez, D.; Rosenberg, R.; Srajer, G. *Physical Review B* **2012**, 86, 035142.

- (14) Radchenko, S.; Petrov, A. *Russian Chemical Reviews* **1989**, 58, 948.
- (15) Gedridge Jr, R. W.; Brandsma, L.; Nissan, R. A.; Verkruijsse, H. D.; Harder, S.; De Jong, R. L.; O'Connor, C. J. *Organometallics* **1992**, 11, 418–422.
- (16) Pöttgen, R.; Dinges, T.; Eckert, H.; Sreeraj, P.; Wiemhöfer, H.-D. *Zeitschrift für Physikalische Chemie* **2010**, 224, 1475–1504.
- (17) Klöss, K.-H.; Hinz-Hübner, D.; Ruschewitz, U. *Zeitschrift für anorganische und allgemeine Chemie* **2002**, 628, 2701–2704.
- (18) Vaughn, T. H.; Nieuwland, J. A. *Journal of the American Chemical Society* **1932**, 54, 787–791.
- (19) Smith, D. M.; Ibers, J. A. *Coordination Chemistry Reviews* **2000**, 200, 187–205.
- (20) Caracelli, I.; Zukerman-Schpector, J.; Pena, J. M.; Stefani, H. A.; Tiekink, E. R. *Acta Crystallographica Section E: Structure Reports Online* **2010**, 66, o685–o685.
- (21) Larson, A.; Dreele, R. V. General Structure Analysis System (GSAS). 2000; Los Alamos National Laboratory Report LAUR 86-748.
- (22) Newville, M. *J. Synchrotron Rad.* **2001**, 8, 322–324.
- (23) Ravel, B.; Newville, M. *J. Synchrotron Rad* **2005**, 12, 537–541.
- (24) The cif files of the fitted crystal structures and the measured XRD spectra in xye format are available as supplementary material. Also available are details of the EXAFS analysis presented in this work.
- (25) Corbett, J. D. *Chemical Reviews* **1985**, 85, 383–397.
- (26) Gielen, M.; Davies, A. G.; Pannell, K.; Tiekink, E. *Tin Chemistry: Fundamentals, Frontiers, and Applications*; Wiley, 2008.

Table 1: Selected crystallographic data²⁴ of A_2TeC_2 ($A=Li,Na$). The $P(C\equiv C)$ and $P(Te-C)$ nearest neighbor distances are projections on the c axis, as the $C\equiv C$ dumbbell carries out a wobbling motion, also observed in other ternary acetylides.¹⁰ Lengths are given in Å, angles in degrees.

	Li_2TeC_2	Na_2TeC_2
Space group	$P\bar{3}m1$	$I4/mmm$
a	6.2981(14)	5.8727(7)
b	6.2981(14)	5.8727(7)
c	4.4987(9)	5.874(4)
α	90.0	90.0
β	90.0	90.0
γ	120.0	90.0
P(Te-C)	1.727	2.333
P($C\equiv C$)	1.044	1.208
A-A	4.131	2.936
A-C	3.665	3.061
A-Te	3.851	3.284
No. of data points	2226	4205
No. of fitting params.	25	19
R_p	0.029	0.034
R_{wp}	0.040	0.046
R_{wp}	0.022	0.028
χ^2	3.312	2.269
$(\Delta/\sigma)_{max}$	3.78	1.44

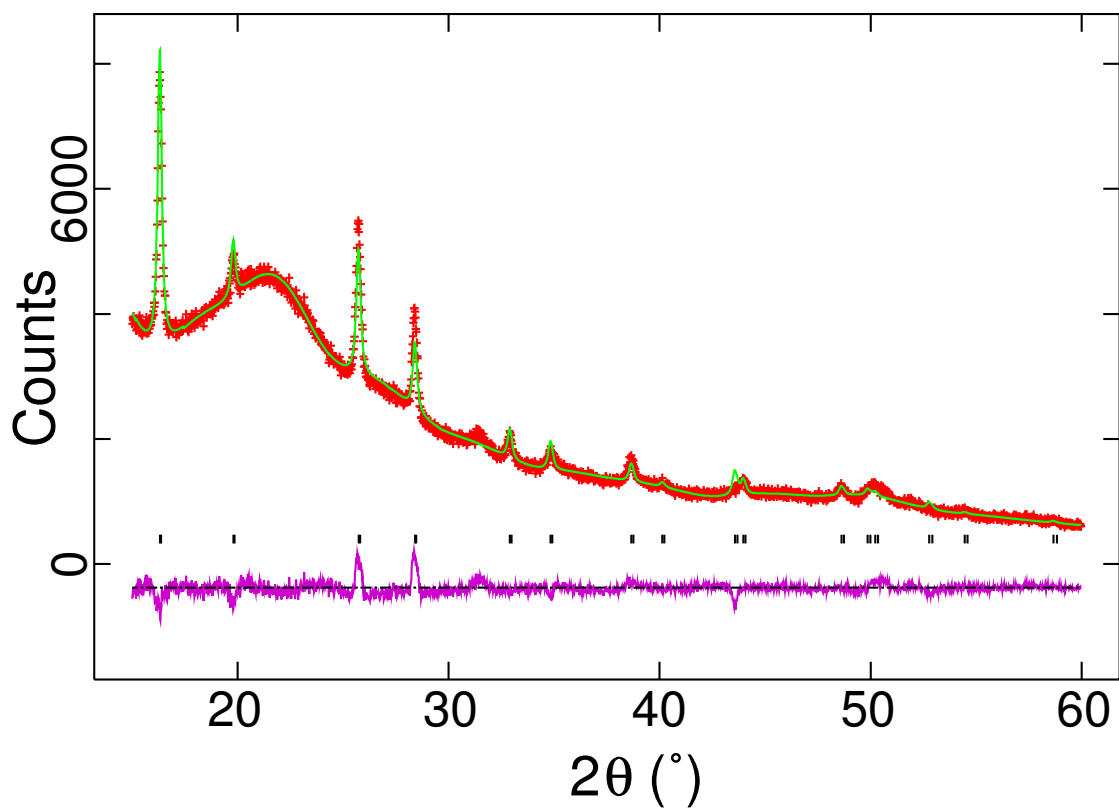


Figure 1: Powder X-ray diffraction spectrum of Li_2TeC_2 (red), the corresponding Rietveld-fit (green) and the difference of experimental and fitted spectra (purple).

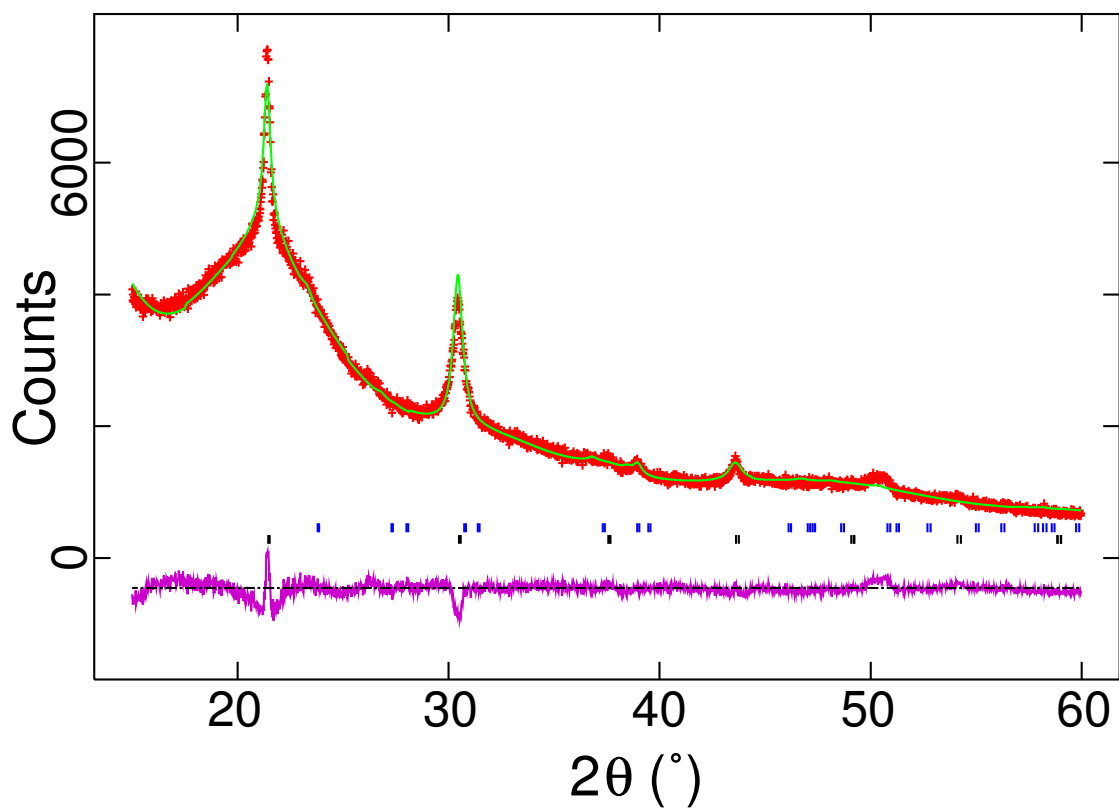


Figure 2: Powder X-ray diffraction spectrum of Na_2TeC_2 (red), the corresponding Rietveld-fit (green) and the difference of experimental and fitted spectra (purple).

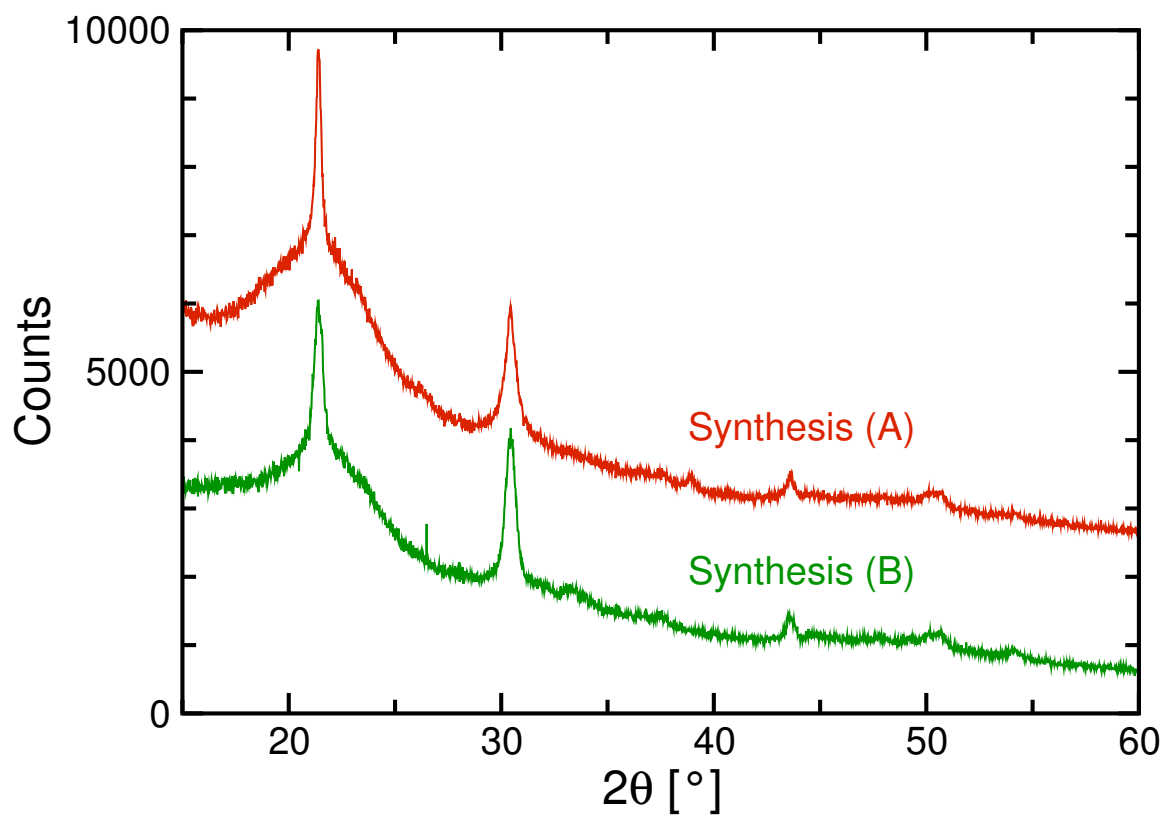


Figure 3: Powder X-ray diffraction spectra of Na_2TeC_2 as obtained by two different synthesis methods. Synthesis (A): $\text{Na}_2\text{C}_2 + \text{Te} \rightarrow \text{Na}_2\text{TeC}_2$. Synthesis (B): $2 \text{NaC}_2\text{H} + \text{Te} \rightarrow \text{Na}_2\text{TeC}_2 + \text{C}_2\text{H}_2$.

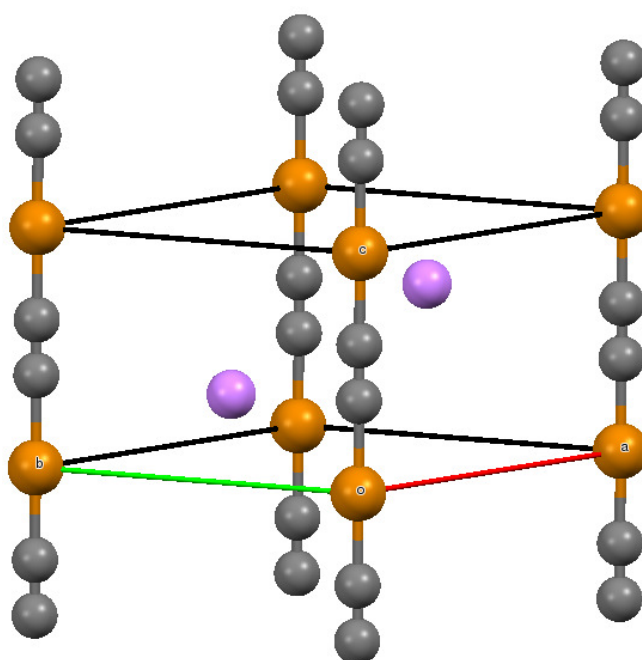


Figure 4: Structure of the Li_2TeC_2 crystal (space group $P\bar{3}m1$) as determined from the powder x-ray diffraction data. Color code: C - gray, Te - bronze, Li - violet.

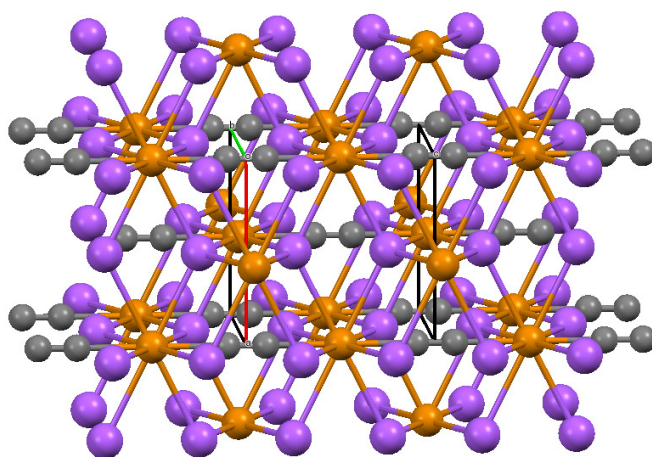


Figure 5: Structure of the Na₂TeC₂ crystal (space group I4/mmm) as determined from the powder x-ray diffraction data. Color code: C - gray, Te - bronze, Na - violet.

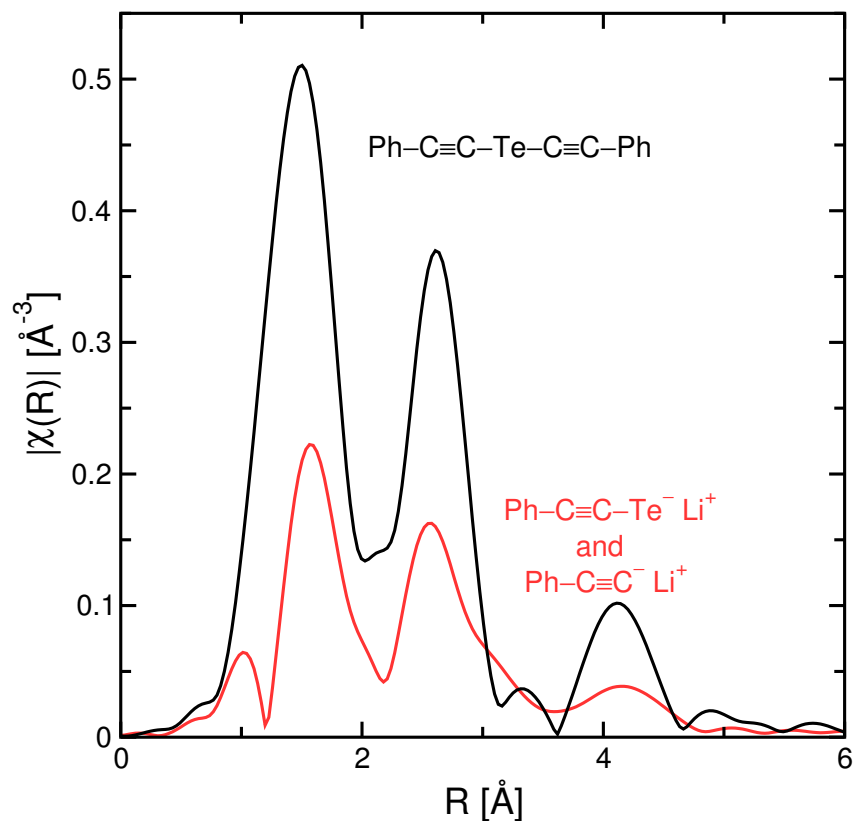


Figure 6: Comparison of the Te K_{α} EXAFS spectra of $\text{Ph-C}\equiv\text{C-Te-C}\equiv\text{C-Ph}$ and its hypothetical double lithiated form. The EXAFS intensities of the double lithiated form are approximately 40% of that of the un lithiated form, indicating that less than half of the phenylacetylene groups are bound to Te, i.e. the double lithiated form is a mixture of $\text{Ph-C}\equiv\text{C-Te}^{-}\text{Li}^{+}$ and $\text{Ph-C}\equiv\text{C}^{-}\text{Li}^{+}$.